

First-principles study of phenyl ethylene oligomers as current-switch

F. Jiang,¹ Y.X. Zhou,¹ H. Chen,^{1,*} R. Note,² H. Mizuseki,² and Y. Kawazoe²

¹*Department of Physics, Fudan University, Shanghai 200433, People's Republic of China*

²*Institute for Materials Research, Tohoku University, Sendai 980-8577, Japan*

(Dated: February 6, 2008)

We use a self-consistent method to study the distinct current-switch of 2'-amino-4-ethynylphenyl-4'-ethynylphenyl-5'-nitro-1-benzenethiol, from the first-principles calculations. The numerical results are in accord with the early experiment [Reed et al., *Sci. Am.* **282**, 86 (2000)]. To further investigate the transport mechanism, we calculate the switching behavior of p-terphenyl with the rotations of the middle ring as well. We also study the effect of hydrogen atom substituting one ending sulfur atom on the transport and find that the asymmetry of I-V curves appears and the switch effect still lies in both the positive and negative bias range.

PACS numbers: 73.23.-b, 85.65.+h, 31.15.Ar

As Moore's law predicted, the density of transistors on integrated circuits doubles approximately every 18 months, and the traditional semiconductor devices will approach to their limit. In this century, the development of electronics may enter a new era of molecular devices. Compared with the traditional solid electronic devices, the molecular devices have many advantages. The molecular chips will be smaller than the silicon chips in three orders and their operation speed will increase evidently without increases in price. The concept of the organic molecular electronic devices was first proposed over a quarter century ago by Aviram and Ratner [1]. However, the molecular devices did not attract much attention until the measurement of the electronic conduction through the single phenyl dithiol (PDT) by Reed et al. in 1997 [2]. From then on, the search for new active molecular devices becomes a worldwide effort [3, 4, 5, 6, 7, 8, 9, 10, 11, 12, 13, 14, 15]. Molecules are intrinsically different from traditional devices, and one expects that some of their transport properties would be unique. An attractive feature of organic molecules for application to electronics is the possibility to control electronic transport by using electrical or photic signal. Several experimental groups reported some molecular switch devices [16, 17, 18], which are mainly included into two categories. One is the electronic switch devices which control the conversion between state "0" and state "1" by the reversible field or the current pulse. The other is the photic switch devices which achieve the open or close states of current by the laser field. Reed et al. [19] used a molecular switch consisting of three aromatic phenyl rings in series. The two hydrogen atoms of the middle ring are substituted by acceptor group NO₂ and donor group NH₂, while the whole molecule is chemisorbed onto the contact surfaces of gold leads. By adjusting the gate voltage, the current can be controlled due to rotation of the middle ring with respect to the side rings. The corresponding theoretical works investigated the similar switch system [20, 21, 22]. However, in these works, the macroscopical electrodes were not

treated on an equal footing with the molecular devices, and the whole open system, lead-molecule-lead, were not treated self-consistently with the charge effect included. In the quantum system, the charge effect is crucial to the transport property. The rigorous treatment of the molecular device calls for combining the theory of quantum transport with the first-principles calculations of the electronic structure. In this article, we use density functional theory (DFT) and nonequilibrium Green's function to study the current-switch behavior of the phenyl ethylene oligomers.

For the lead-molecule-lead system, coupling between the molecule and the leads plays a crucial role in quantum transport. Being computationally tractable, the whole system is partitioned into the molecule part and the lead part, so that these two parts are dealt with separately. The nonequilibrium Green's function theory provides a powerful method to give a full description of transport phenomena. The molecular Green's function is expressed as follows

$$G_M^R = (E^+ S_M - F_M - \Sigma_1^R - \Sigma_2^R)^{-1}, \quad (1)$$

where G_M^R , S_M , F_M are the retarded Green's function, overlap matrix and Fock matrix of the molecule part respectively. Σ_1^R (Σ_2^R), the retarded self-energy of the left (right) electrode, is calculated from the surface Green's function (SGF) g_1^R (g_2^R)

$$\Sigma_i^R = (E^+ S_{Mi} - F_{Mi}) g_i^R (E^+ S_{iM} - F_{iM}), \quad (2)$$

with $i = 1, 2$. The coupling matrices S_{Mi} and F_{Mi} are extracted from the DFT calculation for the extended molecule (molecule with 3 Au atoms on each side).

The density matrix of the open system is the essential function of the whole self-consistent scheme. It can be achieved by the Keldysh Green's function

$$\rho = \int_{-\infty}^{\infty} dE [-iG^<(E)/2\pi], \quad (3)$$

$$-iG^< = G_M^R (f_1 \Gamma_1 + f_2 \Gamma_2) G_M^A, \quad (4)$$

with the advanced Green's function $G^A = (G^R)^\dagger$, the broadening function of the left (right) lead Γ_1 (Γ_2). The Fermi distribution function of the left (right) lead f_1 (f_2) is expressed $f_i(E) = 1/(e^{(E-\mu_i)/kT} + 1)$ with $\mu_1 = E_f - \frac{1}{2}eV$, $\mu_2 = E_f + \frac{1}{2}eV$, we regulate Z axis pointing from the left to the right, so $V > 0$ ($V < 0$) denotes the longitudinal electrical field direction along the positive direction of Z axis (along the negative direction of Z axis). But, this expression is only right for the case that the molecule is symmetrical to the two contacts. If not symmetrical, the voltage drop is also not symmetrical to the two interfaces. Fermi level of the bulk Au is E_f . In our work, E_f is -5.1 eV which is adjusted around its work function (5.31 eV). Since the relative dielectric constant of the molecule is much larger than 1, the voltage drops across the interface between gold atoms and the sulfur atom, while the electronic potential is almost flat. So, the potential zero point can be set at the center of the molecular device.

After obtaining the density matrix self-consistently, we calculate the transmission function $T(E, V)$ of coherent transport

$$T(E, V) = \text{Tr}(\Gamma_1 G^R \Gamma_2 G^A). \quad (5)$$

In order to achieve this goal, we extended the inner loop in the standard quantum chemistry software Gaussian03 [23] to the loop containing the lead-molecule-lead open system under bias. The self-consistent procedure starts from a guess for the density matrix of the open system, which may be obtained from the converged density matrix of Gaussian03 calculation for the isolated molecule. We feedback the density matrix to the Gaussian's main program as a subroutine to obtain the new density matrix. The iterations continue until the density matrix converges to the acceptable accuracy. Then the density matrix is used to evaluate the terminal current and density of states (DOS) of the open system [24, 25]. In the calculations, we adopt DFT with B3PW91 exchange-correlation potential and LANL2DZ basis to evaluate the electronic structure and the Fock matrix. The basis set associates with the effective core potential (ECP), which are specially suited for the fifth-row (Cs-Au) elements with including the Darwin relativistic effect.

In Reed's experiment [19], the middle ring of the molecule 2'-amino-4-ethynylphenyl-4'-ethynylphenyl-5'-nitro-1-benzenethiol can rotate with respect to the side benzene rings under control of the gate voltage. The dipole composed of the acceptor NO_2 and the donor NH_2 , which are attached to the middle benzene, is driven by the external field. Our DFT calculation at LANL2DZ level achieves the optimized molecular structure, where three aromatic phenyl rings are almost in the same plane, the carbon bond length of the alkyne in the middle of two rings is 1.24 Å, the angle of O-N-O is 128° and the angle of H-N-H is 118°. For the sulfur atoms chemisorbed onto the gold leads, there are two kinds of the geometric

configurations. The sulfur atom sits directly on the top position of the surface gold atom or the hollow position of three nearest-neighbor surface gold atoms. As a conventionally accepted picture the latter is adopted in this article. The perpendicular distance between the sulfur atom and the Au FCC (111) surface plane is 2.0 Å, an usually acceptable distance. Due to the precalculation, the temperature effect is not distinct for the short molecule, so, we assume zero temperature in our calculation for simplicity. It is emphasized that since our system is a closed shell system (the number of α electrons is equal to that of β electrons), we adopt restricted calculation which ensures that $\rho^\alpha = \rho^\beta$ in order to spare calculation time. We investigate the molecules under three configurations corresponding to the rotation angle $\alpha = 0^\circ$, 30° , and 60° respectively. DOS and T corresponding to the different values of α are given in Fig. 1, which accounts for the mechanism of the molecular switch. Both HOMO and LUMO are shifted and broadened with the molecule attached by the metallic leads, so that E_f is almost in the middle of HOMO-LUMO gap, a little closer to HOMO, which means electrons will be responsible for the initial rise of the current. The electron incident from the left lead with the energy meeting the one of molecular states will enter the resonant channel. The states with small DOS in the HOMO-LUMO gap is called as the metal-induced gap states (MIGS) arising from the hybridization of gold surface states and molecular HOMO, LUMO states. They offer some electrons (about 0.32 electrons) to the contacts, which causes the molecule to be a system with positive charges. When bias is applied, the system in the nonequilibrium state adjusts its energy levels by the charge effect to prevent the loss of electrons.

The transport characteristics of the molecule-lead system with the rotated configurations are obtained from the DOS curves. The singular points of the Green's function, which are obtained from equation $(F + \Sigma_1 + \Sigma_2)C = SC\lambda$, show the position of the levels of the open system. In the case of $\alpha = 0^\circ$, HOMO is -6.53 eV, LUMO is -3.60 eV, and the HOMO-LUMO gap is 2.93 eV. In the case of 30° , HOMO is -6.54 eV, LUMO is -3.56 eV, and the HOMO-LUMO gap is 2.98 eV. And for 60° , HOMO, LUMO and the HOMO-LUMO gap are -6.73 eV, -3.51 eV, and 3.22 eV, respectively. With the increase in the rotation angle, HOMO and LUMO of the open system keep away from E_f step by step, and the transmission function value at the Fermi level gets smaller. The transmission functions are obtained for the three configurations, $T(E_f) = 0.19 \times 10^{-2}$, 0.14×10^{-2} , 0.34×10^{-3} corresponding to 0° , 30° and 60° . The big rotation angle (e.g. 60°) results in the heavy decrease in the current (the 90° rotation causes the switch into the off state, not shown in the figure) which demonstrates the switchable function of the molecular device. With the molecular device attached by the gold leads, the energy levels are broadened and descend to keep the system electrical-neutral. The electron

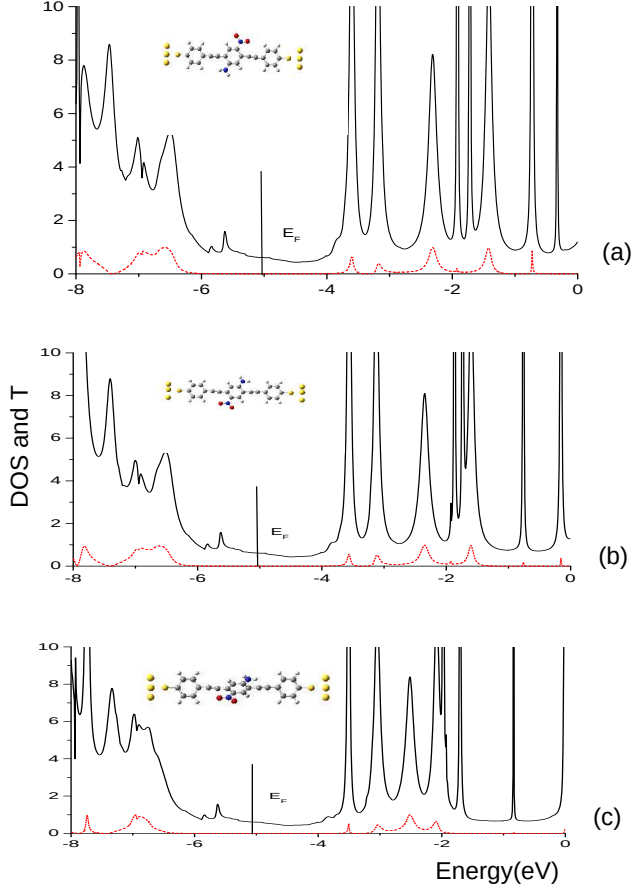


FIG. 1: 2'-amino-4-ethynylphenyl-4'-ethynylphenyl-5'-nitro-1-benzenethiol is chemisorbed onto the gold leads through sulfur atoms from both sides. DOS (solid) and T (dashed) as functions of energy in equilibrium. The vertical line denotes the position of Fermi level. (a) rotation angle $\alpha = 0^\circ$, (b) $\alpha = 30^\circ$, (c) $\alpha = 60^\circ$.

number inside the device decreases from 186 (in the isolated molecule) to 185.6. The basic reason is illustrated by the inset of Fig. 2. The inset shows the energy levels of the isolated molecule corresponding to the three cases. LUMO of the isolated molecule is below the Fermi level, and LUMO+1 is above the Fermi level. With the increase of the rotation angle, LUMO-LUMO+1 gap gets bigger, leading to the same tendency shown in Fig. 1. With leads attached, the charge effect makes the energy levels of the isolated molecule descend and broadened. The LUMO-LUMO+1 gap evolves into the HOMO-LUMO gap of the open system and determines the transport capacity. In Fig. 2 the I-V curves are steep for $\alpha \leq 30^\circ$, since both HOMO and LUMO are responsible for the rising of current. The negative differential resistance (NDR) appears with the added electrons, when bias gets across -3.6 V. From 30° to 60° , the switch effect due to the rotation is more apparent than the case $\alpha \leq 30^\circ$.

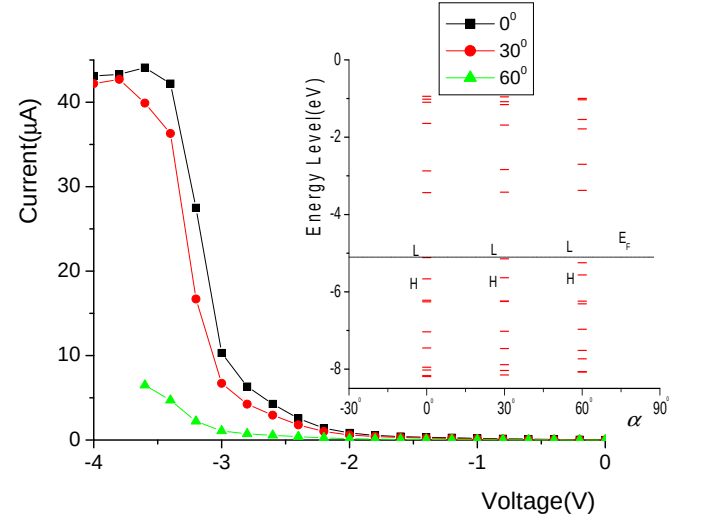


FIG. 2: I-V curves of 2'-amino-4-ethynylphenyl-4'-ethynylphenyl-5'-nitro-1-benzenethiol with gold contacts through sulfur atoms from both sides corresponding to $\alpha = 0^\circ$, 30° and 60° .

The p-terphenyl is a good sample to investigate the molecular switch properties. Fig. 3 gives the I-V curves of p-terphenyl with the anti-clockwise rotations of the middle ring with respect to the side benzenes. In the figure there are five current curves corresponding to rotation angle $\alpha = 0^\circ$, 30° , 45° , 60° , and 90° . The molecular device presents an active switch function, although it is not easy to make it work in practice. The total energies of the isolated molecule corresponding to these angles are -712.967, -712.962, -712.952, -712.938, and -712.924 Hartree, respectively. The energy increases with an increase in the rotation angle, while the molecule with the zero angle is the most stable one. The figure illustrates a distinct switch function. From 0° to 90° , the overlap between π electron clouds decreases with the increase in the rotation angle, which leads the current reduction. For the 0° case, the current of p-terphenyl under the bias 3.0 V is smaller than the one of single PDT, while it is bigger than the latter one above the bias 3.0 V. The abnormal phenomenon comes from the fact that HOMO of p-terphenyl is closer to E_F . The current has a big rise at the point where the voltage gets across HOMO level. The inset shows the molecular orbital pictures of HOMO for rotation angle 0° and 90° . Here, the extended molecule (3 Au atoms on each side are included) is adopted to simulate p-terphenyl connected to gold contacts and its HOMO level has the main contribution to transport in our bias range, while LUMO does not participate in. It is obvious that the HOMO is a delocalized state for 0° and it becomes a localized one when the rotation angle approaches to 90° .

Typically the aromatic phenyl molecule is chemisorbed on the gold surface through a sulfur atom. J. Chen et

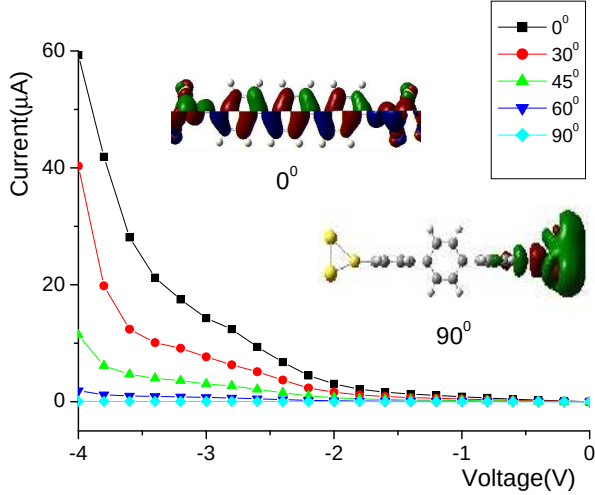


FIG. 3: I-V curves of extended p-terphenyl compound correspond to the different rotation angles. The negative bias means the electrical field is along the direction opposite to the Z axis.

al. [26] once investigated the system with a hydrogen atom to replace the sulfur atom, and obtained a different transport characteristics, since the electronegativity of hydrogen atom is smaller than that of the sulfur atom, which makes the coupling between a hydrogen atom and one gold contact weaker than that between a sulfur atom and the other gold contact. The case is attractive because of the asymmetry of I-V curves [27]. We add a hydrogen atom on the sulfur atom at the right end to make the whole molecule a closed shell system to spare the calculation time, without the intrinsic influence on I-V curve. The distance between hydrogen atom at the left end and gold contact is a little longer than that between sulfur atom and gold contact. But this distance is not clear. We fix this distance at 2.15 Å. The distance between sulfur atom and the other gold contact is still fixed at 2.0 Å. So, the electrostatic potential difference V is divided between the two junctions from the coupling distances: 52% across the H-Au junction and 48% across the S-Au junction. The inset of Fig. 4 gives the energy levels of the isolated molecule with the related HOMO-LUMO gaps: 3.15 eV, 3.23 eV and 3.43 eV for $\alpha = 0^\circ, 30^\circ$ and 60° . The HOMO-LUMO gap increases with the increase in rotation angle, which dominates the transport behavior. Fig. 5 describes DOS and T in equilibrium with the different rotation angle. With the gold leads attached to the molecular device, there are about 181.2 electrons in the device area. Different from the pure S-Au contacts, only LUMO is responsible for the initial rise of the current. With contacts, for the case of 0° , HOMO is -8.03 eV, LUMO is -4.73 eV, and HOMO-LUMO gap is 3.30 eV; for 30° , HOMO is -8.06 eV, LUMO is -4.68 eV, and HOMO-LUMO gap is

3.38 eV; for 60° , HOMO, LUMO and HOMO-LUMO gap are -8.08 eV, -4.62 eV, and 3.46 eV, respectively. The corresponding I-V curves are shown in Fig. 4 for bias region $-1.4 \text{ V} \leq V \leq 3.4 \text{ V}$. The distinct switch effect exists in the small negative bias, while the electron number descends with the increase in bias. The similar switch property occurs in the positive high bias (above 2.0 V) with the electron number variation from 181.2 to 181.6. Because the molecule is not symmetrically connected to the gold contacts, the negative bias is easier to get across LUMO than the positive one and for the negative bias the charge effect does not occur since the left chemistry potential is higher than the right one. Then, LUMO absorbs electrons from the left side, and emits electrons to the right side. The left coupling is weaker than the right one, which keeps LUMO normally unoccupied and results in the descendance of electron number, without the charge effect. So, the current has the initial rise for the small negative bias. For the positive bias, the left chemistry potential is lower than that of the right one, which makes LUMO absorb electrons from the right side and emit electrons to the left one. The abnormally occupied LUMO due to the nonsymmetric coupling causes the rise of electron number. So, the LUMO is kept unoccupied by the charge effect, which results in very small current in the small positive bias range ($V < 2.0 \text{ V}$). With high bias added, the resonant transmission occurred. This process is shown in Fig. 6. With the increase of positive bias from 1.0 V to 3.4 V, the peaks of DOS and T shift to the high energy side continuously. At 3.4 V, the current corresponding to 0° has a sudden rise since the peaks' shift makes both HOMO and LUMO responsible for the transport at this condition. The sudden rise makes the switch effect more apparent in comparison with the case of 60° rotation, where only LUMO is responsible for the rise of the current. Since the distance between the hydrogen atom and the gold contact is not clear, we also calculate the DOS and T of the molecule in equilibrium with the H-Au distance 2.3 Å. Corresponding to $0^\circ, 30^\circ, 60^\circ$, the HOMO-LUMO gaps are 3.31 eV, 3.34 eV, and 3.43 eV respectively. The small change of H-Au distance has little effects on the positions of peaks of DOS and T, only causes current smaller. In fact, even this distance is fixed at 2.9 Å, the switch effect and the asymmetry of I-V curves still exist. Our calculation shows that the asymmetry effect and switch effect are both stable corresponding to the different H-Au distances. We can draw the conclusion: for the LUMO-based molecule, the current is lower for positive bias on the weak contact, while for the HOMO-based molecule, the current is lower for positive bias on the strong contact. The conclusions from the first-principles calculation accord with the previous results obtained by the extended Huckel theory (EHT) [27]. This asymmetry in I-V curves may be used to provide a rectifier.

In summary, we use the self-consistent method based

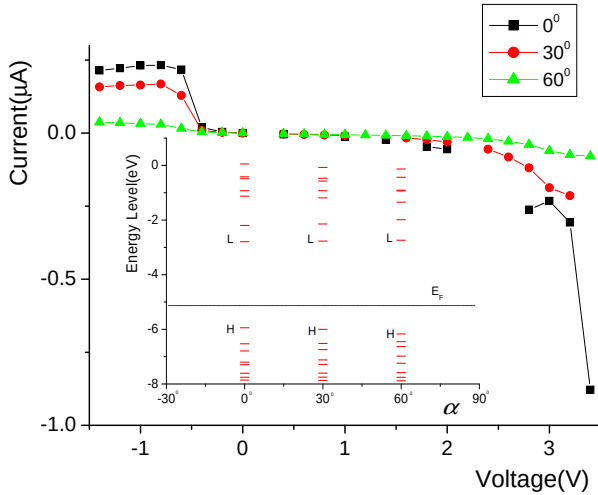


FIG. 4: I-V curves of 2'-amino-4-ethynylphenyl-4'-ethynylphenyl-5'-nitro-1-benzenethiol with gold contacts corresponding to $\alpha = 0^\circ$, 30° and 60° . The atoms that chemisorbed to the gold surfaces are hydrogen atom and sulfur atom respectively. The distance between the ending hydrogen atom and gold contact is 2.15 Å.

on the DFT and the non-equilibrium Green's function to simulate molecular transport. We solve the transport problem from the first-principles theory in order to predict the transport characteristics of some molecular devices and to identify the experimental results from the theoretical point of view. In terms of Gaussian03, the electronic structures for the molecular device and the macroscopic leads are calculated on an equal footing, at the same time, the self-consistent iteration cycle is extended from the local molecule to the open system, by inserting the density matrix of the open system as a subroutine. The self-consistent iteration is run until the density matrix converges within an acceptable accuracy. We investigate the molecular switch reported in the experiment[2], and prove the distinct switch function, theoretically. With one sulfur atom replaced by the hydrogen atom, the switch effect exists in both the low negative bias range and the high positive bias range. The calculation result shows that the asymmetry of I-V curves can be used to make the rectifier. Further study of the influence of gate voltage on molecular transport characteristics is in process.

This work is supported by the National Science Foundation of China (NSFC) under Project 90206031 and 10574024, and Special Coordination Funds of the Ministry of Education, Culture, Sports, Science and Technology of the Japanese Government. The author wants to thank Ph. D candidate Y.Y. Liang for his helpful suggestions. The author would also like to express their sincere thanks to the support from the staff at the Center for Computational Materials Science of IMR Tohoku University for the use of the SR8000 G/64 supercomputer

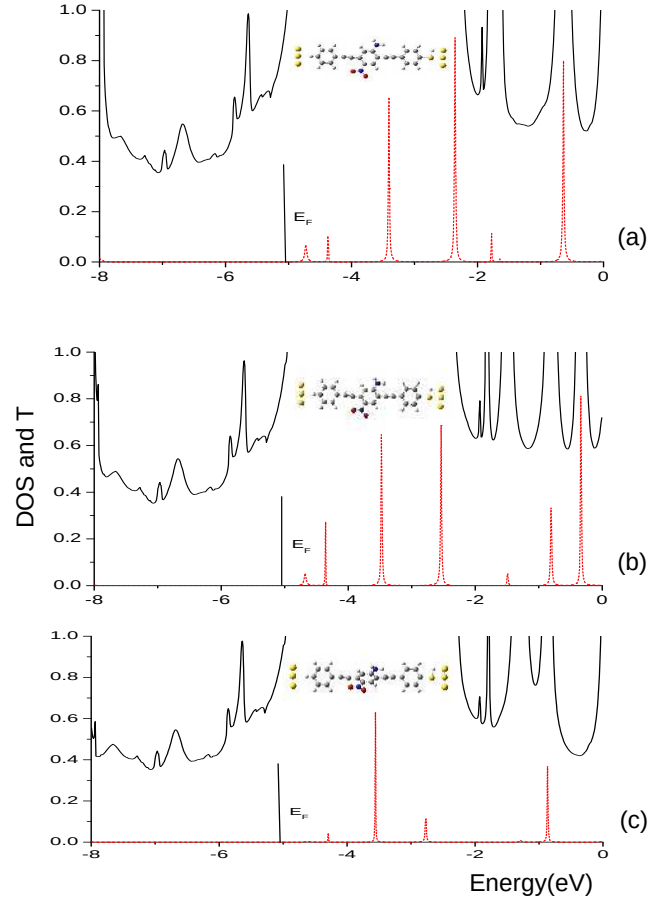


FIG. 5: DOS (solid) and T (dashed) as functions of energy of 2'-amino-4-ethynylphenyl-4'-ethynylphenyl-5'-nitro-1-benzenethiol with gold contacts in equilibrium. The atoms that chemisorbed to the gold surfaces are hydrogen atom and sulfur atom respectively. The distance between the ending hydrogen atom and gold contact is 2.15 Å. The vertical line denotes the position of Fermi level. The rotation angle $\alpha = 0^\circ$ (a), 30° (b), and 60° (c).

facilities.

* Corresponding author. Email: haochen@fudan.edu.cn

- [1] A. Aviram, and M.A. Ratner, Chem. Phys. Lett. **29**, 277 (1974).
- [2] M.A. Reed, C. Zhou, C.J. Muller, T.P. Burgin, and J.M. Tour, Science **278**, 252 (1997).
- [3] D.I. Gittins, D. Bethell, D.J. Schiffrin, and R.J. Nichols, Nature **408**, 67 (2000).
- [4] X.D. Cui, A. Primak, X. Zarate, J. Tomfohr, O.F. Sankey, A.L. Moore, T.A. Moore, D. Gust, G. Harris, S.M. Lindsay, Science **294**, 571 (2001).
- [5] B. Larade, J. Taylor, Q.R. Zheng, H. Mehrez, P. Pomorski, and H. Guo, Phys. Rev. B **64**, 195402 (2001).
- [6] N.B. Zhitenev, H. Meng, and Z. Bao, Phys. Rev. Lett. **88**, 226801 (2002).

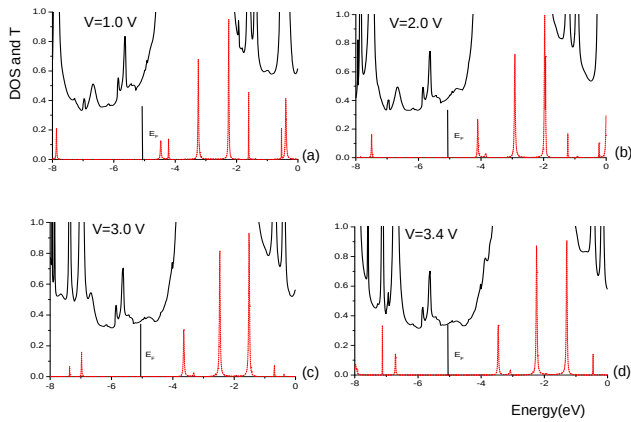


FIG. 6: DOS (solid) and T (dashed) as functions of energy of 2'-amino-4-ethynylphenyl-4'-ethynylphenyl-5'-nitro-1-benzenethiol with gold contacts corresponding to 0° rotation angle with positive bias added. The atoms that chemisorbed to the gold surfaces are hydrogen atom and sulfur atom respectively. The distance between the hydrogen atom and gold contact is $2.15 \text{ \AA}$. The vertical line denotes the position of Fermi level. The added positive bias 1.0 V (a), 2.0 V (b), 3.0 V (c) and 3.4 V (d).

- [7] J. Park, A.N. Pasupathy, J.I. Goldsmith, C. Chang, Y. Yaish, J.R. Petta, M. Rinkoski, J.P. Sethna, H.D. Abruna, P.L. McEuen, and D.C. Ralph, *Nature* **417**, 722 (2002).
- [8] W. Liang, M.P. Shores, M. Bockrath, J.R. Long, and H. Park, *Nature* **417**, 725 (2002).
- [9] R.H.M. Smit, Y. Noat, C. Untiedt, N.D. Lang, M.C. van Hemert, and J.M. van Ruitenbeek, *Nature* **419**, 906 (2002).
- [10] J. Reichert, R. Ochs, D. Beckmann, H.B. Weber, M. Mayor, and H.v. Löhneysen, *Phys. Rev. Lett.* **88**, 176804 (2002).
- [11] R.H.M. Smit, C. Untiedt, G. Rubio-Bollinger, R.C. Segers, and J.M. van Ruitenbeek, *Phys. Rev. Lett.* **91**, 076805 (2002).
- [12] D. Dulic, S.J. van der Molen, T. Kudernac, H.T. Jonkman, J.J.D. de Jong, T.N. Bowden, J. van Esch, B.L. Feringa, and B.J. van Wees, *Phys. Rev. Lett.* **91**, 207402 (2003).
- [13] B. Xu and N.J. Tao, *Science* **301**, 1221 (2003).
- [14] B. Xu, X. Xiao and N.J. Tao, *J. Am. Chem. Soc.* **125**, 16164 (2003).
- [15] X. Xiao, B. Xu, and N.J. Tao, *Nano Lett.* **4**, 267 (2003).
- [16] H.G. Heller, *IEE Proc.* **130**, 209 (2000).
- [17] Z.F. Liu, K. Hashimoto and A. Fujishima, *Nature* **347**, 658 (1990).
- [18] P.E. Kornilovitch, A.M. Bratkovsky, and R.S. Williams, *Phys. Rev. B* **66**, 245413 (2002).
- [19] M.A. Reed, J.M. Tour, *Sci. Am.* **282**, 86 (2000).
- [20] J.M. Seminario, P.A. Derosa, and J.L. Bastos, *J. Am. Chem. Soc.* **124**, 10266 (2002).
- [21] R. Pati and S.P. Karna, *Phys. Rev. B* **69**, 155419 (2004).
- [22] S.M. Hou, J.X. Zhang, R. Li, J. Ning, R.S. Han, Z.Y. Shen, X.Y. Zhao, Z.Q. Xue and Q.D. Wu, *Nanotechnology* **16**, 239 (2005).
- [23] M.J. Frisch et al., *Gaussian 03, Revision B. 04*, (Gaussian, Inc., Pittsburgh PA, 2003).
- [24] P.S. Damle, A.W. Ghosh, S. Datta, *Chem. Phys.* **281**, 171 (2002).
- [25] F. Jiang, Y.X. Zhou, H. Chen, R. Note, H. Mizuseki and Y. Kawazoe, *Phys. Rev. B* **72**, 155408 (2005).
- [26] J. Chen, T. Lee, J. Su, W. Wang, M.A. Reed, A.M. Rawlett, M. Kozaki, Y. Yao, R.C. Jagessar, S.M. Dirk, D.W. Price, J.M. Tour, D.S. Grubisha, D.W. Bennett, in *Molecular Nanoelectronics*, M.A. Reed and T. Lee, Eds., (American Scientific Publishers, CA, 2003).
- [27] A.W. Ghosh, F. Zahid, P.S. Damle and S. Datta, *cond-mat/0202519* (2002).